

Nanoscale Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. Pinna, E. Cali, G. Kerherve, G. Galleri, M. Maggini, P. Innocenzi and L. Malfatti, *Nanoscale Adv.*, 2020, DOI: 10.1039/D0NA00048E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Fulleropyrrolidine-functionalized ceria nanoparticles as a tethered dual nanosystem with improved antioxidant propertiesAlessandra Pinna,^a Eleonora Cali,^a Gwilherm Kerherve,^a Grazia Galleri,^b Michele Maggini,^c Plinio Innocenzi,^d Luca Malfatti^{*d}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Dual-tethered nanosystems which combine different properties at the nanoscale represent a new fascinating frontier of research. In the present work, we present an example of dual nanosystem designed to enhance the radical scavenging performances. Fulleropyrrolidine has been bonded to cerium oxide nanoparticles (nanoceria) to form a dual tethered system. The fulleropyrrolidine, bearing a silyl-alkoxide group, have been chemically bonded to the nanoceria surface, providing an unprecedented antioxidant activity. This effect has been evaluated using L929 mouse fibroblast cell line exposed to UV light. The fulleropyrrolidines tethered to the nanoceria enhance the radical scavenging properties of the oxide. At the same time, fulleropyrrolidine mitigates the potential toxicity of the nanoceria at high doses. On the other hand, cerium oxide nanoparticles provide a strong hydrophilic character to the dual nanosystem, ensuring the administration in a cellular environment and preventing macroscopic aggregation of the fulleropyrrolidine. The rational assembly of two different components in one nanosystem appears as a promising route for the development of “smarter” medical and cosmetic devices.

Introduction

Cerium oxide nanoparticles have grabbed increasing attention because of the UV-shielding and radical scavenging properties.^{1–6} Cerium oxide is a semiconductor with wide band-gap capable of strong absorption in all the three regions of the UV light (UV-A, B, and C, respectively).⁷ Cerium oxide, synthesized in the form of nanoparticles, shows an autocatalytic activity, being the Ce atoms able to switch between the 3+ and 4+ oxidation state.⁸ This property has put the cerium oxide nanoparticles on the spotlight because the autocatalytic activity leads to a strong radical-scavenging effect when this phenomenon occurs in a biological environment at pH 7.4. Several research groups have reported the beneficial effects of nanoceria when applied to cardio-, neuro-protective and radiation therapies⁹ or the prevention of retinal degeneration induced by reactive oxygen species (ROS).^{10–12} Although the promising applications, the use of nanoceria in biomedicine is still controversial.¹³

The autocatalytic effect, in particular conditions, can turn the nanoceria from a radical scavenger to a radical former.¹⁴ This can make nanoceria at high doses a toxic drug for several types of cells, converting the nanoparticles into a carcinogenic compound.¹⁵ At present, the administration dose and the nanoparticle size seem to be crucial parameters to modulate the nanoceria response when it is used in a biological environment. Larger particles tend to produce radicals while smaller particles are more prone to neutralize these species.^{16–18} The reasons for this dual behaviour reside in the relative amount of Ce³⁺ and Ce⁴⁺ on the nanoparticle surface. A full design of the system properties, therefore, requires extremely accurate control of their size,¹⁹ with an error smaller than a nanometer. This explain why the use of nanoceria as a drug for medical therapies would be difficult without using surface functionalization or core-shell structures.

On the other hand, fullerene-based materials have proved to be an efficient radical scavenging when exposed to UV, X- or even γ -rays.²⁰ Fullerene molecules can attract and neutralize 20 or more free radicals per molecule with better performances than vitamin C and vitamin E. The radical scavenging effect is due the conjugated double bonds of the molecule. The low-lying lowest unoccupied molecular orbital (LUMO) can easily accept an electron from the reacting radicals. The radical scavenging process appears to be catalytic, allowing the fullerene to react with many superoxides without being consumed. Due to this property, fullerenes have been defined as radical sponges.^{21,22} This property envisages that fullerene and its derivatives (such as fulleropyrrolidine) could be successfully applied to prevent

^a Department of Materials, Imperial College London, South Kensington Campus, London, SW72BP.

^b Department of Chemistry and Pharmacy, CR-INSTM, University of Sassari, 07100, Sassari, Italy. *Correspondence autor: luca.malfatti@uniss.it

^c Department of Clinical and Experimental Medicine University of Sassari, 07100, Sassari, Italy

^d Department of Chemical Sciences University of Padova, 35131, Padova, Italy.

Electronic Supplementary Information (ESI) available: [Raman spectrum of the substrate, TEM images of CeO₂ nanoparticles, DLS of Si-Fulp/ceria, Si-Fulp and ceria in ethanol, details about the calculation method for determining the weight percentage of Si-Fulp in the dual nanosystem and the Ratio of Si-Fulp molecules with respect to ceria nanoparticles, NMR ¹H ¹³C and MALDI-TOF of fulleropyrrolidine]. See DOI: 10.1039/x0xx00000x



sensitive materials from UV-degradation and biological tissues from ROS overproduction.^{23,24} In previous years, antiviral activity of the fullerene has been extensively investigated and directly correlated with the unique anti-oxidant properties of its molecular structure.²⁵ Aqueous C₆₀ suspensions, for instance, have shown to protect the liver of rodents against free-radical damage, without causing acute or subacute toxicity.²⁶

In this work, we have designed a tethered dual nanosystem capable of merging the radical scavenging properties of the cerium oxide nanoparticles and fullerene-derivatives. We have used a fulleropyrrolidine bearing an ethoxy-silyl group to increase the solubility of fullerene in an aqueous environment and enable the functionalization of inorganic materials, as shown in previous work.²⁷

This new system is expected to mitigate the eventual risk coming from the use of naked cerium oxide nanoparticles. The functionalization of cerium oxide nanoparticles with functional molecules, in fact, has already proved to be a successful strategy in both cosmetic and medical applications.²⁸ Nanoceria, for instance, has been at functionalized with branched polyethylenimine and then reacted with genipin (a natural molecule extracted from *Gardenia jasminoides*) to formulate a cosmetic made of pigmented nanoparticles with improved free radical scavenging activity.²⁹ Ceria nanoparticles, functionalized with dextran and loaded with curcumin, have been capable of inducing a substantial cell death in neuroblastoma cell.³⁰ Finally, Prussian Blue-functionalized nanoceria has been applied in ultrasensitive detection of the tumour necrosis factor- α .³¹ All these applications, however, make use of a polymer to coat the nanoparticles. After this step a second functional species, such as a molecule or a dye, is attached.

In our work, Nanoceria has been functionalized with a fulleropyrrolidine, bearing an alkoxy-silyl group, through a chemical bonding. This functionalization provides a partial solubility of the fullerene molecules and ensures close proximity to the ceria nanoparticle surface. The tethered dual nanosystem has been characterized and tested as a protecting device towards a UV insult for a specific type of cell line, L929 mouse fibroblast. The combination of two distinct types of nanomaterials to form multifunctional nanodevices is an innovative strategy. This approach would allow the development of medical applications and a new generation of cosmetics with improved efficacy.

Results and discussion

Efficient protection to UV light by the ceria - fulleropyrrolidine (Si-Fulp/ceria) system relies on an effective functionalization of the nanoceria with the organic molecules. To achieve this target, we have used a silylated-fulleropyrrolidine bearing three terminal ethoxide groups. These functions have been at first hydrolyzed by acid catalysis in ethanol to form -OH groups and then reacted with the OH-Ce of the nanoceria surface to

induce polycondensation. **Fig. 1** shows the chart of the overall reaction.

DOI: 10.1039/D0NA00048E

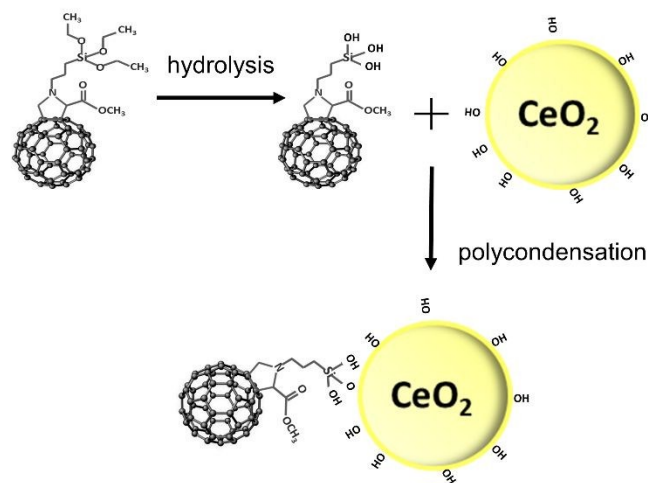


Fig. 1 Diagram of the nanoceria functionalization with Si-Fulp.

Although the polycondensation reactions can also occur among different Si-Fulp molecules, after several purification cycles, we have observed an evident change in the colour of the nanoceria. It forms a pale-yellow solution which turns into light brown after functionalization. To assess the structure and composition of the system, we have used a combination of different characterization techniques. Raman spectroscopy, in particular, has been used to assess the functionalization of nanoceria surface with Si-Fulp. **Fig. 2** shows the Raman spectra in the 1700–150 cm⁻¹ range of nanoceria, Si-Fulp, and Si-Fulp/ceria.

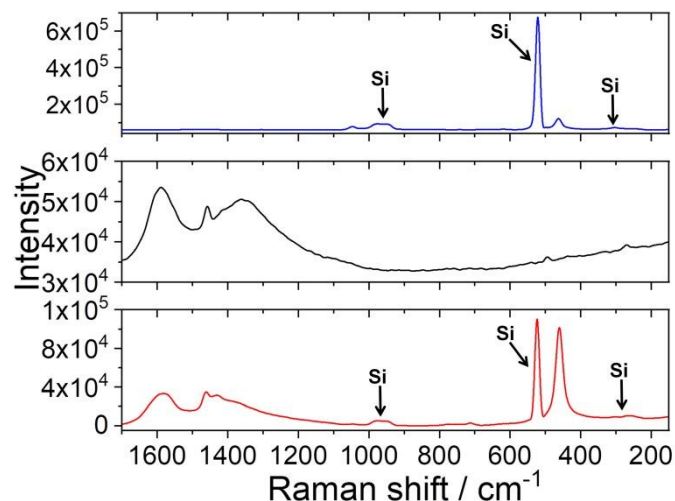


Fig. 2 Raman spectra in the 1700 – 150 cm⁻¹ range of nanoceria (blue line), the pristine Si-Fulp (black line) and nanoceria functionalized with Si-Fulp (red line). The bands at 303, 523 and 965 cm⁻¹ are due to the monocrystalline silicon substrate.



The Raman spectrum of bare nanoceria deposited onto silicon wafer (**Fig. 2**, blue line) exhibits asymmetric band at 464 cm^{-1} which is assigned to the symmetric breathing mode of the Ce–O vibrational unit in the crystalline cerium oxide with a cubic fluorite structure.^{32,33} The band peaked at 1049 cm^{-1} has been attributed to residual and unreacted CeNO₃ used as nanoceria precursor.³⁴ The dimension of ceria crystallites (D) has been estimated by using the Full-Width Half Maximum (FWHM) of the band at 464 cm^{-1} and applying the following formula:³⁵

$$FWHM(\text{cm}^{-1}) = 10 + \frac{124.7}{D}$$

By this method, the dimension of ceria nanoparticles has resulted to be 10.8 nm. The other bands which appear in the spectrum (303 , 523 and 965 cm^{-1}) are due to the monocrystalline silicon substrate (see ESI, **Fig. S1**). The spectrum of Si-Fulp (**Fig. 2**, black line) is characterized by three absorption bands peaking at 1431 cm^{-1} H_g(7); 1456 cm^{-1} , A_g(2); 1581 cm^{-1} , H_g(8), which are associated to the stretching mode of the cages of C₆₀.³⁶ The Si-Fulp/ceria spectrum (**Fig. 2**, red line) shows both signals of nanoceria and Si-Fulp suggesting the successful functionalization of the cerium oxide nanoparticles. Compared with the pure Si-Fulp spectrum, the Raman bands related to C₆₀ in the Si-Fulp/ceria spectrum are slightly shifted to lower wavelength by 3 cm^{-1} . The shift is attributed to the strong interaction between the nanoceria and the chemically grafted Si-Fulp.³⁷

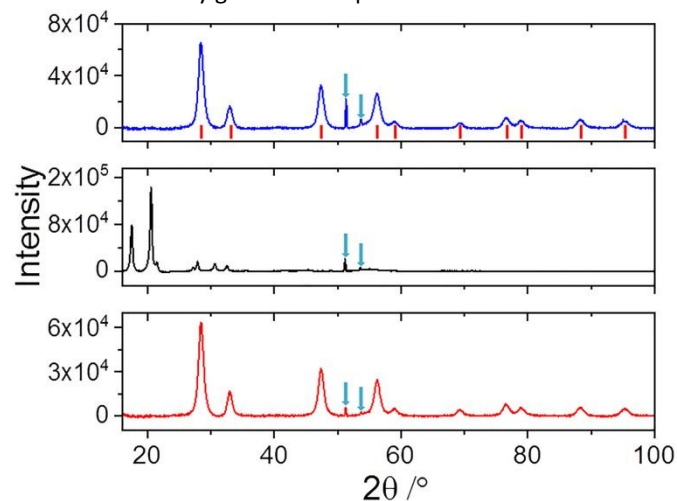


Fig. 3 XRD patterns of nanoceria (blue line), Si-Fulp (black line) and Si-Fulp/ceria (red line) in the 15–100 2θ range. The red ticks show the standard diffraction peaks of fluorite CeO₂ (JCPDS No. 34-0394). Nanoceria crystallite dimension was calculated by Scherrer equation considering the diffraction peaks at 2θ 28, 33 and 47 in 2θ . The sharp diffraction peaks (down arrows) at 51.3 and 53.6 in 2θ are due to the silicon substrate.

Fig. 3 shows the XRD patterns relative to the nanoceria (blue line), Si-Fulp (black line), and the Si-Fulp/ceria (red line).

Nanoceria shows the typical diffraction pattern of face-centered cubic CeO₂ (JCPDS No. 34-0394), with the fluorite structure. [(111), (200), (220), (311), (222), (400), (331), (420) planes at $2\theta = 28.5, 33.1, 47.5, 56.3, 59.1, 69.4, 76.7, 79.1, 88.4, \text{ and } 95.3^\circ$]. The crystallite dimension, as calculated by Scherrer equation, resulted to be $\approx 7.8 \pm 0.4\text{ nm}$. This size is compatible with TEM measurements of the naked nanoceria (see ESI, **Fig. S2**). The Si-Fulp XRD pattern corresponds to a crystallized face-centred cubic lattice of C₆₀ with the diffraction plane (111), (220), (311), (222), (331), (420), (442) and (333) at $10.6, 12.3, 17.5, 20.6, 24.5, 27.2, 27.9, 30.7, 32.5\text{ }2\theta$ angles.³⁸ Finally, the pattern of Si-Fulp-grafted nanoceria only shows the diffraction peaks attributed to cerium oxide, proving that no residual Si-Fulp crystals remained after functionalization and purification.

High-resolution TEM (HR-TEM) image in **Fig. 4a** reveals the self-assembly of Si-Fulp into amorphous aggregates when reacted with nanoceria in water solution. The Fast Fourier Transform (FFT) of the TEM image (**Fig. 4a**) has confirmed the cubic nature of the crystalline nanoceria with an average size of $\approx 7\text{ nm}$. An interplanar spacing of $d=0.19\text{ nm}$, corresponding to the (220) plane, has been measured.

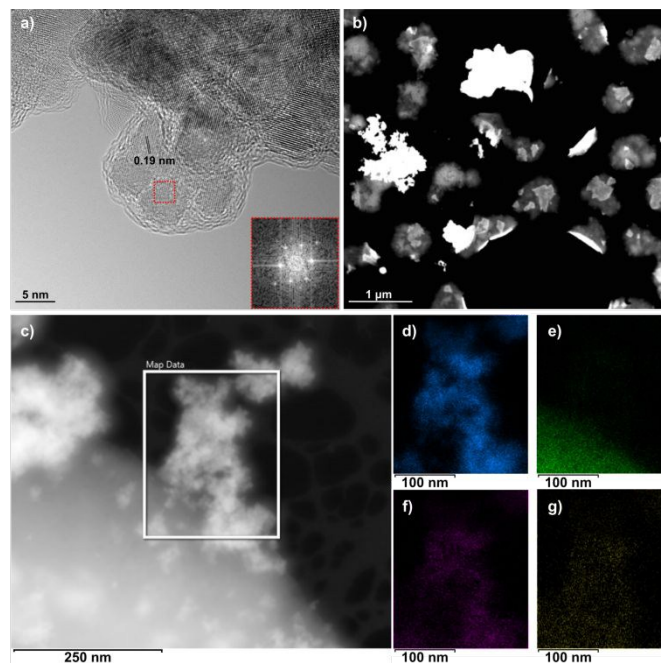


Fig. 4 a) HR-TEM and b) DF-STEM images of Si-Fulp/ceria. The inset in a) shows the FFT obtained on the nanoceria (red-boxed region) with a d -spacing of 0.19 nm. c) Transmission electron image of Si-Fulp/ceria. EDS elemental maps of d) Ce, e) C, f) O, g) Si obtained on the boxed region in c).

The Si-Fulp covers the cerium oxide nanoparticles surface, as shown in **Fig. 4a**, and an amorphous layer surrounds a small aggregate of nanoparticles. Cid et al. have in fact demonstrated the capability of fullerene-based structure to



self-organize into different shapes as a function of the dispersing solvent.³⁹ Furthermore, the aggregates in the dark field STEM image of **Fig. 4b** clearly show a difference in contrast due to the change in the material composition. The bright (and therefore denser) regions correspond to the crystalline nanoceria; the darker aggregate surrounding the nanoceria corresponds to the amorphous self-assembled Si-Fulp. **Fig. 4d-g** shows the elemental distribution of the Si-Fulp/ceria (the selected area in **Fig. 4c**). The analysis confirms the functionalisation of nanoceria with Si-Fulp. In particular, EDS measurements have confirmed that the amorphous aggregate visible in the selected area of **Fig. 4c** is fulleropyrrolidine grafted on the nanoceria surface (C map, **Fig. 4e**). The fullerene compound is bound to the nanoceria particles aggregate (Ce and O maps, **Fig. 4d,f**) through the silanol tail (Si map, **Fig. 4g**).

The aggregation state of the Si-Fulp-grafted nanoceria has also been studied by dynamic light scattering. The measures show that the ceria nanoparticle and Si-Fulp in ethanol have an average size of the aggregate of 47.18 ± 11.52 and 323 ± 63.42 nm, respectively. After functionalization, the Si-Fulp-grafted nanoceria aggregates increase in size with an average value of 619.7 ± 116 nm. The size distribution plots of the three samples are reported in ESI, **Fig. S3**. Both Si-Fulp/ceria and nanoceria remain stable in water solutions for long time. **Fig. S4** (ESI) shows a picture of the two solutions after 3 months from the synthesis.

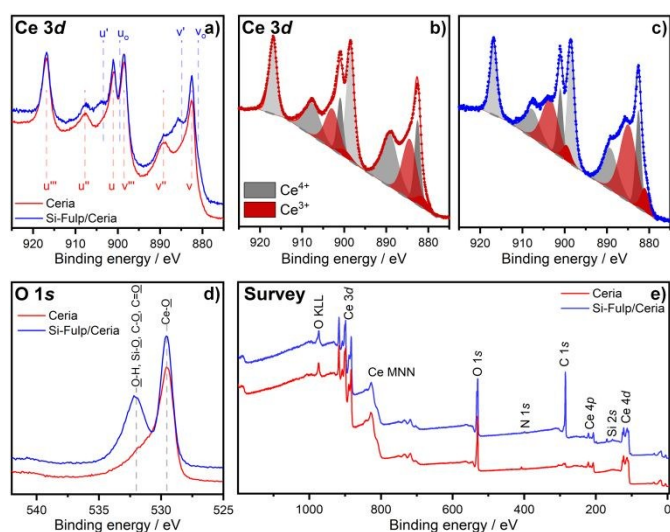


Fig. 5 a) Ce 3d spectra of the bare nanoceria (red) and Si-Fulp/ceria (blue). For comparison, both samples were normalised to the peak noted (u''') at B.E. of 916.8 eV. Deconvoluted Ce 3d spectra of the b) bare nanoceria and c) Si-Fulp/ceria. d) O 1s spectra and e) survey spectra of the bare nanoceria (red) and Si-Fulp/ceria (blue).

The concentration of Ce^{3+} and Ce^{4+} has been evaluated in both species by using XPS. **Fig. 5a** shows the Ce 3d core level of the nanoceria and the Si-Fulp/ceria. In the case of the nanoceria,

six peaks are observed, namely v, v'', v''', u, u' and u''' . They are attributed to the tetravalent form of Ce in CeO_2 and with a spin orbit splitting of ~ 18.5 eV.⁴⁰⁻⁴³ After functionalization of the nanoceria with Si-Fulp, two shoulders appear at 884.9 eV (v') and 903.4 eV (u') corresponding to the satellite peaks of the Ce 3d in its trivalent form.^{40,43} This clearly suggests that the functionalisation of Si-Fulp promotes the formation of Ce^{3+} site at the surface of the ceria nanoparticles. **Fig. 5b-c** shows a detailed view of the deconvoluted Ce 3d spectra used to calculate the concentration of Ce^{3+} and Ce^{4+} . The concentration of Ce^{3+} increases from 31% to 43% in bare bone nanoceria and Si-Fulp/ceria, respectively, while Ce^{4+} decreases from 69% to 57%. It was observed that nanoceria can act both as superoxide dismutase (SOD), by neutralizing superoxide radicals, and catalase (CAT), by promoting the decomposition of hydrogen peroxide into water and oxygen.⁴⁴ According to the literature, an increase in Ce^{3+}/Ce^{4+} ratio provides mimetic properties to Si-Fulp/ceria which are more similar to SOD than CAT.⁴⁴

The O 1s spectrum of (**Fig. 5d**) shows the onset of the band picked at 532 eV, when nanoceria is functionalised with Si-Fulp. This band is related to the presence of OH group onto the nanoceria surface whereas the other band at 530 eV is attributed to the lattice oxygen.⁴⁵ Ce^{3+} ions, which are mostly present at nanoceria surface, are active sites for the reaction.⁴⁶ Especially in aqueous solution, the cerium ions can act as catalytic sites for H_2O dissociation, resulting in the formation of $-OH$ surface groups.⁴⁷ The OH group is capable of forming strong Ce-O-Si- bonding with silicate ions ($-Ce-OH+Si-O \leftrightarrow -Ce-O-Si- + OH^-$).⁴⁸ The XPS data clearly proved the nanoceria surface functionalization with Si-Fulp throughout oxygen bond. The survey scan (**Fig. 5e**), measured from 0 to 1200 eV, has shown binding energies assigned to cerium, oxygen, silicon, carbon and nitrogen. This indicates the purity of the samples.

The amount of Si-Fulp grafted onto the nanoceria has been estimated by thermogravimetric analysis (TGA) of nanoceria, Si-Fulp, and Si-Fulp/ceria (**Fig. 6**). The blue line shows the multistage thermal decomposition of nanoceria; the first step (198 °C) corresponds to the urea conversion into liquid ammonia isocyanic acid (HNCO) while the second (303 °C) is related to the rapid vaporization of ammonia as a consequence of the HNCO hydrolysis.⁴⁹ In the range between 370-600 °C, the mass loss is attributed to the conversion of residual $Ce(OH)_3$, which is on the nanoceria surface, into CeO_2 .⁵⁰

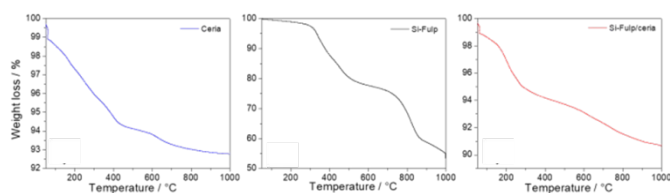


Fig. 6 TGA analysis of nanoceria (blue line), Si-Fulp (black line) and Si-Fulp/ceria (red line) in air at a heating rate of 10 °C



min⁻¹.

The thermogravimetric curve of Si-Fulp (Fig. 6, black line) shows a first weight loss (531°C) assigned to the decomposition of the alkoxides which in the functionalization group of fulleropyrrolidine.⁵¹ The second weight loss, occurring from 535 to 865 °C, is assigned to the structural degradation of the fulleropyrrolidine, in agreement with previous findings.⁵² The multistage decomposition of Si-Fulp/ceria particles is a combination of the features shown by the two previous materials, i.e. nanoceria and Si-Fulp (Fig. 6, red line). The weight loss of Si-Fulp/ceria has allowed calculating the weight % of Si-Fulp bound to nanoceria as 4.7%. Furthermore, considering the average size of the nanoceria and the density of cerium dioxide, the ratio between the Si-Fulp-grafted molecules and the number of nanoceria can be estimated as 39.5, indicating that the amount of the fulleropyrrolidine molecules is higher than the number of cerium oxide nanoparticles in the tethered nanosystem. The details of the calculation, as derived from TGA, are available as Electronic Supporting Information. Although the ratio between Si-Fulp-grafted molecules and nanoceria is quite high, we cannot exclude the presence of bare cerium oxide nanoparticles after the functionalization process.

The UV-Visible absorption spectroscopy has been used to assess the functionalization of nanoceria with the Si-Fulp. Fig. 7a shows the typical absorption spectrum of Si-Fulp: the absorption bands peaking at 212, 255 and 321 nm are assigned to the C₆₀ dipole-allowed transition⁵³ while the very weak band at 430 nm, is typical of 1,2-dihydrofullerens.⁵⁴ The spectrum of nanoceria is characterized by two absorption bands, one at 210 nm and a second one at 327 nm corresponding to the Ce 4f-O 2p and Ce 5d-O 2p valence states.⁵⁵ The bandgap, calculated by the Tauc method, is 3.12 eV. The Si-Fulp/ceria spectrum shows a combination of absorption bands attributed to Si-Fulp and nanoceria with a strong band at 210 nm and a second large band peaked around 300 nm. Si-Fulp/ceria, when dissolved in water, shows a red shift of the absorption bands (250 and 314 nm respectively) which further increases as a function of the solution concentration. Moreover, above 350 nm, we observe an increase in absorbance due to the increase of Ce³⁺ formed during the surface functionalization (Fig. 7b).⁵⁶ The radical scavenging property of fulleropyrrolidine combined with the autocatalytic activity of cerium oxide nanoparticles creates an unprecedented antioxidant effect when the Si-Fulp/ceria nanosystem are dispersed in a liquid environment. This property has been at first tested by a chemical assay with 2-Diphenyl-1-picrylhydrazyl (DPPH) and then confirmed by in vitro test with L929 mouse fibroblast exposed to a UV insult. The DPPH molecule in water forms a radical with specific absorption at 517 nm.

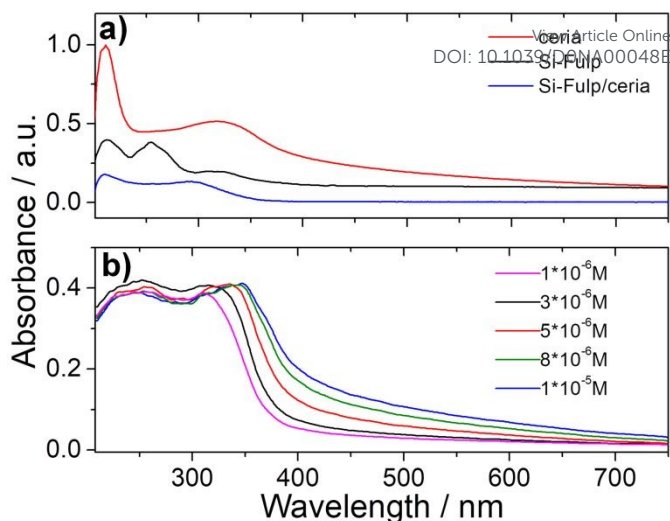


Fig. 7 a) UV-Vis spectroscopy of nanoceria, Si-Fulp and Si-Fulp/ceria in water solution. b) UV-Vis spectra of Si-Fulp/ceria in water at different concentrations.

This allows monitoring the radical scavenging properties of a specific compound by measuring the UV-Visible spectroscopy of the absorbing radical molecule. Fig. 8 shows the change in intensity as a function of time of the 327 and 517 nm absorption bands (0.078 mg mL⁻¹ Si-Fulp/ceria concentration). The spectra show a progressive decrease in intensity of the absorption bands with the increase of time.

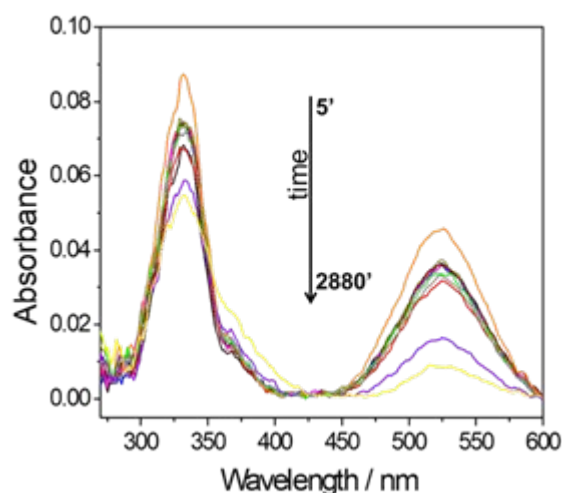


Fig. 8 UV-Vis spectroscopy of a Si-Fulp/ceria dispersed in DPPH water solution (0.078 mg mL⁻¹) as a function of time (min.).

A similar trend is observed by monitoring the intensity decrease of the 517 nm absorption band as a function of the Si-Fulp/ceria concentration (Fig. 9a, red line, and 9b). The same experiment has been also performed with bare cerium



oxide nanoparticles for comparison (Fig. 9a, blue line). The observed trend suggests that when Si-Fulp is grafted on the nanoceria, the percentage of radical inhibition increases of about 10%, therefore improving the potential of the nanoceria as a radical scavenger. This is due to the mutual effect of Si-Fulp and nanoceria, which are both contributing to the radical scavenging.

Finally, the antioxidant activity and cytotoxicity of both nanoceria and Si-Fulp/ceria have been evaluated *in vitro* by flow cytometry assay using L929 mouse fibroblast cells. L929 cells have been exposed to increasing concentration of nanoparticles (0.05 mg mL⁻¹, 0.1 mg mL⁻¹ and 1.5 mg mL⁻¹) for 24 and 48 hours. After the incubation with nanoparticles, the cells were exposed to UV light ($\lambda = 265$ nm) for 1 hour to simulate an oxidative insult. The antioxidant protection of both nanoceria and Si-Fulp/ceria against reactive species has been assessed by measuring the viability of the cells after exposure to UV. Fig. 10 shows the average results obtained from these experiments. The top left of Fig. 10 shows no significant difference in apoptosis at 24h between the control (CTRL) and cells treated with nanoceria at all concentrations. On the contrary the same cells, exposed to the UV, show a significant difference in apoptosis at all nanoceria concentrations with respect to the UV control with $p < 0.001$; the higher the nanoceria concentration, the lower the apoptosis. From these preliminary results we can assess that nanoceria, especially at 1.5 mg mL⁻¹, is capable of protecting the cells from the UV insult.

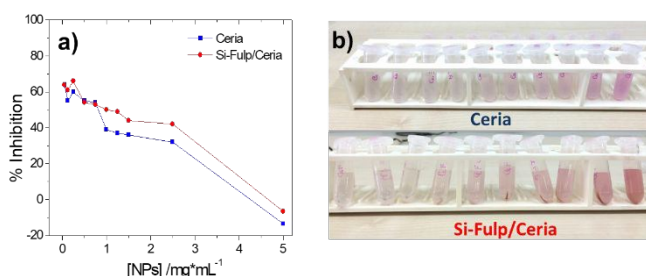


Fig. 9 a) Change in intensity of the 517 nm band vs. nanoceria concentration (blue line) and Si-Fulp/ceria concentration (red line). b) Decoloration of the nanoceria and Si-Fulp/ceria solutions as a function of the antioxidant concentration.

Moreover, the functionalisation of nanoceria with Si-Fulp (top right Fig. 10) empowers the protective effect at all used concentrations of the dual-tethered nanosystem against the UV insult. In this second graph the statistical difference ($p < 0.001$) is expressed with a dose-dependent trend both in the exposed (orange bars) and not exposed (blue bars) cells, with the exception of the sample treated with 0.05 mg mL⁻¹ vs CTRL, where no significant difference has been calculated.

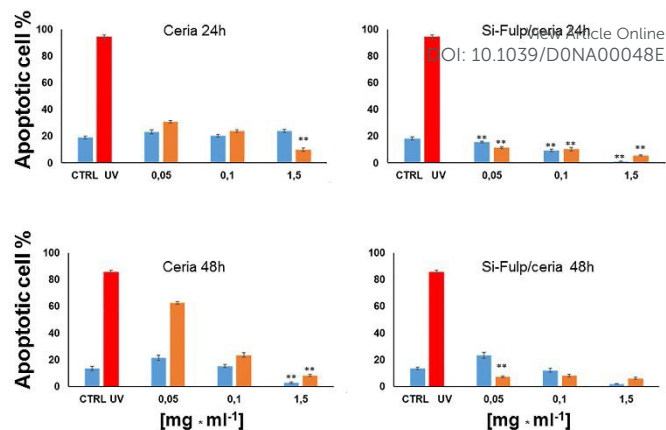


Fig. 10 Bar graphs showing the percentage of apoptotic L929 mouse fibroblast cells *in vitro* treated with different concentration of nanoceria and exposed to UV irradiation for 24h (top graphs) and 48h (bottom graphs). Orange and light blue bars refer to UV-irradiated and not UV-irradiated cells, respectively. Red bar refers to the control, irradiated with UV and not treated with nanoceria. Asterisks indicate statistically significant differences between nanoceria-treated L929 cells vs CTRL ($p < 0.01$).

In the bottom left of Fig. 10 (Ceria 48h), a significant increase in apoptosis is observed between cells treated with nanoceria (both exposed and not-exposed) and the control ($p < 0.001$). In the cells not-exposed to UV, apoptosis decreases with increasing nanoceria concentration ($p < 0.001$). The presence of Si-Fulp on the nanoceria surface dramatically decreases apoptosis in UV-exposed cells with respect to samples without Si-Fulp (Fig. 10, bottom right). This highlights the ability of the dual-tethered nanosystem to provide greater protection against UV. The reduction of apoptosis is so evident already at the concentration of 0.05 mg mL⁻¹ of ceria-Si-Fulp with mild, but significant, decreases in apoptosis at higher concentrations. On the other hand, by comparing the sample not exposed to the UV insult, we observe no differences in apoptosis between samples treated with Si-Fulp or not-treated. In fact there is the same significant difference of apoptosis, which is dose-dependent, towards the controls, both in presence or without Si-Fulp. This evidence suggests that the Si-Fulp/ceria is a highly efficient nanosystem to protect against radicals and it is very well tolerated by the L929 cells.

Experimental

Synthesis of Nanoceria

Cerium(III) nitrate hexahydrate ($\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$, ABCR 99.9%), urea ($\text{CH}_4\text{N}_2\text{O}$, Aldrich 99%), 2-propanol (99.7%, Carlo Erba), 1 M hydrochloric acid (HCl, Aldrich), 5 M aqueous ammonia (NH_4OH , Aldrich), ethanol (EtOH, Fluka 99.8%), 2,2-Diphenyl-1-picrylhydrazyl (DPPH, Aldrich 99%), methanol (MeOH, Aldrich, 99.8%) were used as received without further purification.



Urea was used as coordinating agent, NH_4OH and $\text{Ce}(\text{NO}_3)_3$ as inorganic precursors.

7.00 g of $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ were dissolved in 20 mL of 2-propanol, then 0.5 mL of 1M HCl were added and stirred until complete dissolution. In a separate vial, 2.00 g of urea were dissolved into 20 mL of 2-propanol containing 0.5 ml of HCl 1M and stirred for 5 min. The urea solution was then added, dropwise, to the $\text{Ce}(\text{NO}_3)_3$ solution under stirring, and when the addition was complete, 14 mL of NH_4OH (aq) were added to the mixture. Afterwards, the solution was exposed to microwaves (4 times at 600 W for 10 s), washed with water and centrifuged at 10000 rpm. The supernatant was discarded and a light yellow milky pellet (1.12 g CeO_2) was dispersed in 10 mL of water (nanoceria stock suspension, 112 mg mL^{-1}).

Synthesis of alkoxy-silyl-fulleropyrrolidine

Fulleropyrrolidine (Si-Fulp) (Chart 1) was synthesized according to the work of Bianco et al.,⁵⁸ it was characterized by NMR and MALDI-TOF (see ESI Fig. S5 and S6).

Nanoceria functionalization with Si-Fulp (Si-Fulp/ceria)

10 mg of Si-Fulp was dissolved in 750 μL of EtOH and 50 μL of HCl 1N. The dispersion was sonicated at room temperature until complete dissolution. In a separate vial, 50 mg of nanoceria (450 μL of nanoceria stock suspension) were dispersed in 200 μL of deionized water and mixed with a Si-Fulp solution which was sonicated in an ultrasound bath for 1 hour at 60 °C. Later on the Si-Fulp/ceria nanoparticles were washed 3 times with water and centrifuged at 5000 rpm. After the third washing step the supernatant was completely transparent, indicating the removal of unreacted Si-Fulp molecules. The supernatant was therefore discarded and the pellet was dispersed in 1 mL of water.

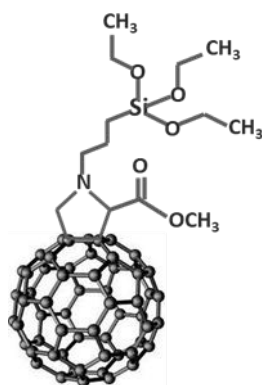


Chart 1.

Antioxidant activity

The antioxidant activity of nanoceria and Si-Fulp/ceria was evaluated by 2,2-Diphenyl-1-picrylhydrazyl (DPPH) radical-scavenging assays. DPPH is a free radical, stable at room temperature, which produces a violet solution in methanol. This free radical is reduced in the presence of an antioxidant molecule, giving rise to colorless methanol solution.

In detail the reaction mixture containing 750 μL of nanoceria and Si-Fulp/ceria aqueous solutions at different concentrations (0.078, 0.195, 0.39, 0.78, 1.17, 1.56, 1.95, 2.34, 3.9, 7.8 mM) were incubated with 375 μL of DPPH methanol solution (0.05 mM). After 5 minutes the samples were centrifuged at 5000 rpm for other 3 min and the supernatant was measured by UV-Vis spectrophotometer at 517 nm fixed wavelength. The mixture of 750 μL of water and 375 μL of MeOH corresponds to the blank while the mixture of 750 μL of water and 375 μL of DPPH is the control. The DPPH decoloration, which is correlated to the scavenging activity (SA %), was calculated by the following formula using the absorbance (Abs) of the sample and the control:

$$\text{SA\%} = [(\text{Abs control} - \text{Abs sample}) / \text{Abs control}] * 100$$

Characterization

The crystalline structure and nanoparticles dimension were characterized by X-ray diffraction spectroscopy using Bruker D8 discover instrument in grazing incidence geometry with a Cu $\text{K}\alpha$ line ($\lambda = 1.54056 \text{ \AA}$); the X-ray generator worked at a power of 40 kV and 40 mA. The patterns were recorded in 2θ ranging from 10 to 100° with a step size of 0.05° and a scan speed of 0.5 s by a repetition mode for 12 h until maximization of the signal-to-noise ratio.

A Raman microscope was used to study the functionalization of nanoceria with Si-Fulp. A Bruker Senterra confocal Raman microscope working with a laser excitation wavelength of 532 nm at 12 mW of nominal power was used for optical microscopy (100× magnification) and Raman spectroscopy analysis; the spectra were recorded by averaging 30 acquisitions of 2 s.

Thermogravimetric analysis was performed using a TA Instrument SDT Q600 thermobalance with alumina crucibles. Nanoceria, Si-Fulp, and Si-Fulp/ceria powder were dried at 60°C for 24 h and placed into the crucibles. The measurement was done using 38.79 mg of nanoceria, 36.72 mg of Si-Fulp/ceria and 2.37 mg of Si-Fulp in a nitrogen flow of 100 mL min^{-1} with a 5 °C min^{-1} heating rate over the temperature range 22–1000°C.

The UV-Visible absorption spectra were recorded using Nicolet Evolution 300 UV-Vis spectrophotometer working in intelliscan mode; UV-grade silica glass (Heraeus) has been used as background reference.

Aggregate size of nanoceria, Si-Fulp and Si-Fulp/ceria in solution was investigated using Dynamic Light Scattering (DLS, Malvern instrument 2000). Before the DLS measurements the dried particles were dissolved in ethanol (1.8 mg mL^{-1}) and sonicated in the sonication bath for 30 min.

Moreover, the samples were analysed by transmission electron microscopy (TEM) using a JEOL JEM-2100F TEM operating at a 200 kV voltage and a FEI Titan operating at a 300 kV voltage equipped with a Cs aberration image corrector. Chemical composition of the samples was determined through energy dispersive X-ray spectroscopy (EDS) operated in scanning-transmission electron microscopy (STEM) mode (EDS 80 mm X-Max detector, Oxford Instruments). Specimens for TEM analysis were prepared by sonication of powder samples in DI water subsequently drop-casted on holey carbon film copper grids (3.05 mm diam. 300 mesh, TAAB).

The surface chemistry of the nanoceria material was analysed by X-ray Photoelectron Spectroscopy (XPS). XPS spectra were



recorded on a Thermo Scientific K-Alpha+ X-ray photoelectron spectrometer operating at 8×10^{-9} mbar base pressure. This system incorporates a monochromated, micro-focused Al K α X-ray source ($h\nu = 1486.6$ eV) and a 180° double focusing hemispherical analyzer with a 2D detector. The X-ray source was operated at 6 mA emission current and 12 kV anode bias providing an X-ray spot size of up to 400 μm^2 . Core level spectra were recorded at 20 eV pass energy and surveys at 200 eV pass energy. A flood gun was used to minimize the sample charging that occurs when exposing an insulated sample to an X-ray beam. Deconvolution of Ce 3d spectra was performed using the Casa XPS software. A linear background was subtracted to the data and peaks were fitted using a product of gaussian and Lorentzian ratio. The binding energy (B.E.) was corrected by aligning the C 1s peak of the adventitious carbon (C-C) at 284.8 eV.

Cell Culture

NCTC clone 929 Clone of strain L (also known as L929; ECACC 85011425) were obtained from the European Collection of Authenticated Cell Cultures (London, UK). Cells were cultured as a monolayer in Dulbecco's modified Eagle medium (DMEM, Sigma-Aldrich, USA) containing 2 mM L-glutamine, 10% fetal bovine serum (FBS, Sigma-Aldrich), 20 U penicillin, and 20 μg streptomycin mL $^{-1}$ (Sigma-Aldrich) at 37°C in a humidified incubator with 5% CO $_2$.

Cells treatment with nanoparticles

The cells were washed with Dulbecco's phosphate-buffered saline (PBS, Bioshop, UK) and detached from the flask's surface using 0.25% trypsin with 0.02% EDTA (Sigma-Aldrich, Poland). Cells were cultured in a 24 well cell culture tray, and when the cells were 75-80 % confluent (approximately 2×10^5 cells /well) treated with increasing concentration of nanoparticles (0.05 mg mL $^{-1}$, 0.1 mg mL $^{-1}$ and 1.5 mg mL $^{-1}$) for 24 and 48 hours. After the incubation with nanoparticles, the cells were exposed or not exposed to UV light ($\lambda = 265$ nm) for 1 hour to simulate an oxidative insult. Afterwards L929 were detached from the cultured well, washed with PBS and collected in 12 x 75 mm flow cytometric tubes. Subsequently, L929 fibroblast cells were stained with Annexin V-APC Apoptosis Kit (BD Pharmingen™ Cat no 556547) and with propidium iodide (PI).

Cell Apoptosis Assay

Annexin V and PI staining were used to quantify the number of apoptotic cells. L929 fibroblast cells were collected and washed twice with PBS. After centrifuging, the cells were resuspended in 500 μL of binding buffer in a flow cytometric tube. Soon after 5 μL of Annexin V-FITC and 5 μL of PI were added to the cells suspension, mixed well and incubated for 15 min at room temperature in the dark. The stained cells were acquired by FACS Canto (Becton Dickinson, San Jose, USA) flow cytometry and analysed by Diva Software 6.3. 30.000 total events were acquired for each experimental point and the percentage of early and late apoptotic and necrotic cells were analysed with GraphPad Prism 7.0 software.

Conclusions

Combining the properties of nanoceria and fulleropyrrolidine at the nanoscale is a challenging and innovative approach to improve the rational design of functional materials.

Fulleropyrrolidine bearing an alkoxy-silyl group is an efficient modifier of the cerium oxide nanoparticle surface, and the Si-Fulp/ceria dual system is a novel class of tethered nanomaterials with improved functionalities. The dispersion of the fulleropyrrolidine molecules is, however, limited by their solubility. The tethered dual nanosystem shows an improved antioxidant activity when added to water or biological media containing radical species although the presence of not-functionalized nanoceria could lead to an underestimate of this effect. In addition, the cytotoxicity of Si-Fulp/ceria is strongly mitigated with respect to high doses of nanoceria. This is a direct result of the coupling with the fulleropyrrolidine. Our approach, which involves the rational design of dual systems, tethered at the nanoscale, is a further step towards the development of advanced devices for healthcare and cosmetics.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

University of Sassari is also acknowledged for funding through "fondo di ateneo per la ricerca 2019".

References

- H. J. Kwon, D. Kim, K. Seo, Y. G. Kim, S. I. Han, T. Kang, M. Soh, T. Hyeon, Ceria Nanoparticle Systems for Selective Scavenging of Mitochondrial, Intracellular, and Extracellular Reactive Oxygen Species in Parkinson's Disease. *Angew. Chem.* 2018, **57**, 9408.
- H. J. Kwon, M.-Y. Cha, D. Kim, D. K. Kim, M. Soh, K. Shin, T. Hyeon, I. Mook-Jung, Mitochondria-Targeting Ceria Nanoparticles as Antioxidants for Alzheimer's Disease. *ACS Nano* 2016, **10**, 2860.
- F. Corsi, F. Caputo, E. Traversa, L. Ghibelli, Not Only Redox: The Multifaceted Activity of Cerium Oxide Nanoparticles in Cancer Prevention and Therapy. *Front. Oncol.* 2018, **8**, 309.
- S.M. Hirst, A.S. Karakoti, R.D. Tyler, N. Sriranganathan, S. Seal, C.M. Reilly. S.M. Hirst, A.S. Karakoti, R.D. Tyler, N. Sriranganathan, S. Seal, C.M. Reilly. Anti-inflammatory properties of cerium oxide nanoparticles. *Small.* 2009, **5**, 2848. *Small.* 2009, **5**, 2848.
- A. Karakoti, S. Singh, J. M. Dowding, S. Seal, W. T. Self. Redox-active radical scavenging nanomaterials. *Chem. Soc. Rev.* 2010, **39**, 4422.
- S. Das, S. Singh, J.M. Dowding, S. Oommen, A. Kumar, T.X. Sayle, S. Saraf, C.R. Patra, N.E. Vlahakis, D.C. Sayle, W.T. Self, S Seal. The induction of angiogenesis by cerium oxide nanoparticles through the modulation of oxygen in intracellular environments. *Biomaterials.* 2012, **33**, 7746.
- A. Dhall, W. Self, Cerium Oxide Nanoparticles: A Brief Review of Their Synthesis Methods and Biomedical Applications *Antioxidants* 2018, **7**, 97.
- A. Pinna, C. Figus, B. Lasio, M. Piccinini, L. Malfatti, P. Innocenzi, Release of ceria nanoparticles grafted on hybrid organic-inorganic films for biomedical application. *ACS Appl. Mater. Interfaces* 2012, **4**, 3916.
- J. Colon, N. Hsieha, A. Fergusona, P. Kupelian, S. Seal, D. W. Jenkins, C. H. Baker. Cerium oxide nanoparticles protect gastrointestinal epithelium from radiation-induced damage



- by reduction of reactive oxygen species and upregulation of superoxide dismutase 2. *Nanomedicine*. 2010, **6**, 698.
- 10 G. A. Silva, Seeing the benefits of ceria. *Nature Nanotech.* 2006, **1**, 92.
- 11 C. Xu, X. Qu, Cerium oxide nanoparticle: a remarkably versatile rare earth nanomaterial for biological applications. *NPG Asia Mater.* 2014, **6**, e90.
- 12 F. Caputo, M. Mameli, A. Sienkiewicz, S. Licocchia, F. Stellacci, L. Ghibelli, E. Traversa, A novel synthetic approach of cerium oxide nanoparticles with improved biomedical activity. *Sci. Rep.* 2017, **7**, 4636.
- 13 R. A. Yokel, S. Hussain, S. Garantziotis, P. Demokritou, V. Castranova, F. R. Cassee, The yin: an adverse health perspective of nanoceria: uptake, distribution, accumulation, and mechanisms of its toxicity. *Environ. Sci.: Nano*, 2014, **1**, 406.
- 14 H. J. Eom and J. Choi, Oxidative stress of CeO₂ nanoparticles via p38-Nrf-2 signaling pathway in human bronchial epithelial cell, Beas-2B. *Toxicol. Lett.*, 2009, **187**, 77.
- 15 M. T. Tseng, Q. Fu, G. K. Lorc, R. Fernandez-Botran, Z.-B. Deng, U. M. Graham, D. A. Butterfield, E. A. Grulke, R. A. Yokel, Persistent Hepatic Structural Alterations Following Nanoceria Vascular Infusion in the Rat. *Toxicol. Pathol.*, 2014, **42**, 984.
- 16 A. Pinna, B. Lasio, M. Piccinini, B. Marmiroli, H. Amenitsch, P. Falcaro, Y. Tokudome, L. Malfatti, P. Innocenzi, Ceria nanoparticles for the treatment of Parkinsonlike diseases induced by chronic manganese intoxication. *ACS Appl. Mater. Interfaces* 2013, **5**, 3168.
- 17 N. M. Zholobak, V. K. Ivanov, V. K.; A. B. Shcherbakov, A. S. Shapovov, O. S. Polezhaeva, A. Y. Baranchikov, N. Y. Spivak, Y. D. Tretyakov, UV-shielding property, photocatalytic activity and photocytotoxicity of ceria colloid solutions. *J. Photochem. Photobiol. B* 2011, **102**, 32.
- 18 H. Xiang, Y. Chen, Energy-Converting Nanomedicine. *Small* 2019, **15**, 1805339.
- 19 A.S. Karakoti, N.A. Monteiro-Riviere, R. Aggarwal, J.P. Davis, R.J. Narayan, W.T. Self, J. McGinnis, S. Seal. Nanoceria as Antioxidant: Synthesis and Biomedical Applications. *JOM*. 2008, **60**, 33.
- 20 G. V. Andrievsky, V. I. Bruskov, A. A. Tykhomyrov, S. V. Gudkov, Peculiarities of the antioxidant and radioprotective effects of hydrated C₆₀ fullerene nanostructures in vitro and in vivo. *Free Radic. Biol. Med.* 2009, **47**, 786.
- 21 P. J. Krusic, E. Wasserman, P. N. Keizer, J. R. Morton, K. F. Preston, Radical reactions of C₆₀. *Science* 1991, **254**, 1183.
- 22 A. Pinna, L. Malfatti, M. Piccinini, P. Falcaro, P. Innocenzi, Hybrid materials with an increased resistance to hard X-rays using fullerenes as radical sponges. *J. Sync. Rad.* 2012, **19**, 586.
- 23 F. Ariu, L. Bogliolo, A. Pinna, L. Malfatti, P. Innocenzi, L. Falchi, D. Bebbere, S. Ledda, Cerium oxide nanoparticles (CeO₂ NPs) improve the developmental competence of in vitro-matured prepubertal ovine oocytes. *Reprod. Fert. Develop.* 2017, **29**, 1046.
- 24 S. M. Hirst, A. S. Karakoti, R. D. Tyler, N. Sriranganathan, S. Seal, C. M. Reilly, Anti-inflammatory properties of cerium oxide nanoparticles. *Small* 2009, **5**, 2848.
- 25 R. Partha, J. L. Conyers, Biomedical applications of functionalized fullerene-based nanomaterials. *Int. J. Nanomedicine*, 2009, **4**, 261.
- 26 N. Gharbi, M. Pressac, M. Hadchouel, H. Szwarc, S. R. Wilson, F. Moussa, Fullerene is a powerful antioxidant in vivo with no acute or subacute toxicity. *Nano Lett.* 2005, **5**, 2578.
- 27 P. Innocenzi, P. Falcaro, S. Schergna, M. Maggini, E. Menna, H. Amenitsch, J. A. A. Soler-Illia, D. Grosso, C. Sanchez. One-pot self-assembly of mesostructured silica films and membranes functionalised with fullerene derivatives. *J. Mater. Chem.* 2004, **14**, 1838. View Article Online
DOI: 10.1039/D0NA00048E
- 28 N. Thakur, P. manna, J. Das, Synthesis and biomedical applications of nanoceria, a redox active nanoparticle. *J. Nanobiotechnol.* 2019, **17**, 84.
- 29 I. Selestin Raja, N. Duraipandi, Manikantan Syamala Kiran, Nishter Nishad Fathima, An emulsion of pigmented nanoceria as a medicinal Cosmetic *RSC Adv.*, 2016, **6**, 100916.
- 30 I. Kalashnikova, J. Mazar, C. J. Neal, A. Rosado, S. Das, T. Westmoreland, S. Seal. Nanoparticle delivery of Curcumin induces Cellular Hypoxia and ROS-mediated Apoptosis via modulation of Bcl-2/Bax in human Neuroblastoma. *Nanoscale*, 2017, **9**, 10375.
- 31 T. Li, Z. Si, L. Hu, H. Qi, M. Yang. Prussian Blue-functionalized ceria nanoparticles as label for ultrasensitive detection of tumor necrosis factor- α . *Sens. Actuators B Chem.* 2012, **171–172**, 1060.
- 32 A. Pinna, L. Malfatti, G. Galleri, R. Manetti, S. Cossu, G. Rocchitta, R. Migheli, P. A. Serra, P. Innocenzi, Ceria nanoparticles for the treatment of Parkinson-like diseases induced by chronic manganese intoxication. *RSC Adv.* 2015, **5**, 20432.
- 33 P. Sridharan, G. Vinothkumar, P. Pratheesh, K. S. Babu. Modulation of biomimetic properties of cerium oxide nanoparticles by hypoxic tumor microenvironments: steering towards tumor specificity. *New J. Chem.*, 2018, **42**, 6370.
- 34 J. T. Miller, D. E. Irish, Can, Infrared and Raman spectra of the cerium(IV) ion – nitrate ion – water system. *J. Chem.* 1967, **45**, 147.
- 35 I. Kosack, V. Petrovsky, M. Anderson, P. Colombar, Raman Spectroscopy of Nanocrystalline Ceria and Zirconia Thin Films. *J. Am. Ceram. Soc.*, 2002, **85**, 2646.
- 36 W. Zhang, X. Gong, C. Liu, Y. Piao, Y. Sun, G. Diao, Water-soluble inclusion complex of fullerene with γ -cyclodextrin polymer for photodynamic therapy. *J. Mater. Chem. B.* 2014, **2**, 5107.
- 37 X. Zhang, Y. Huang, Y. Wang, Y. Ma, Z. Liu, Y. Chen, Global Atmospheric Emissions of Polycyclic Aromatic Hydrocarbons from 1960 to 2008 and Future Predictions. *Carbon* 2008, **47**, 313.
- 38 B. M. Ginzburg, Sh.Tuocchiev, S. Kh. Tabarov, A. A. Shepelevskioe, L. A. Shibaev, X-ray Diffraction Analysis of C₆₀ Fullerene Powder and Fullerene Soot. *Tech Phys.* 2005, **11**, 1458.
- 39 A. Cid, Ó. A. Moldes, M. S. Diniz, B. Rodríguez-Gonzalez, J. C. Mejuto, Redispersión and Self-Assembly of C₆₀ Fullerene in Water and Toluene. *ACS Omega* 2017, **2**, 2368.
- 40 A. Kotani, T. Jo, J.C. Parlebas, Many-body effects in core-level spectroscopy of rare-earth compounds. *Adv. Phys.* 1988, **37**, 37.
- 41 P.A. Connor, X. Yue, C. D. Savaniu, R. Price, G. Triantafyllou, M. Cassidy, G. Kerherve, D. J. Payne, R. C. Maher, L. F. Cohen, R. I. Tomov, B. A. Glowacki, R. V. Kumar, J. T. S. Irvine. Tailoring SOFC Electrode Microstructures for Improved Performance. *Adv. Energy Mater.* 2018, **8**, 1800120.
- 42 R.C. Maher, G. Kerherve, D.J. Payne, X. Yue, P.A. Connor, J. Irvine, L.F. Cohen, The Reduction Properties of M-Doped (M=Zr, Gd) CeO₂/YSZ Scaffolds Co-Infiltrated With Nickel. *Energy Technol.* 2018, **6**, 1.
- 43 A. Pfau, K. D. Schierbaum. Electronic structure of stoichiometric and reduced CeO₂ surfaces: An XPS UPS and HREELS study. *Surf. Sci.* 1994, **321**, 71.
- 44 S. Barkam, S. Das, S. Saraf, R. McCormack, D. Richardson, L. Atencio, V. Moosavifazel, S. Seal. The Change in Antioxidant Properties of Dextran-Coated Redox Active Nanoparticles Due to Synergetic Photoreduction–Oxidation. *Chem. Eur. J.* 2015, **21**, 12646.



- 45 P. Janoš, J. Henych, J. Pfeifer, N. Zemanová, V. Pilařová, D. Milde, T. Opletal, J. Tolasz, M. Malýd, V. Štengl. Nanocrystalline cerium oxide prepared from a carbonate precursor and its ability to breakdown biologically relevant organophosphates. *Environ. Sci. Nano*, 2017, **4**, 1283.
- 46 C.T. Campbell, C.H. Peden. Oxygen vacancies and catalysis on ceria surfaces. *Science*. 2005, **309**, 713.
- 47 L. Kundakovic, D.R. Mullins, S.H. Overbury. Adsorption and reaction of H₂O and CO on oxidized and reduced Rh/CeOx(111) surfaces, *Surf. Sci.* 2000, **457**, 51.
- 48 J. Seo, J. Moona, J. H. Kima, K. Lee, J. Hwanga, H. Yoon, D. K. Yid, U. Paika. Role of the oxidation state of cerium on the ceria surfaces for silicate adsorption. *Appl Surf Sci*, 2016, **389**, 311.
- 49 K. Mathrmool, A. Akkarapongtrakul, S. Sukkum, T. Bongkarn, Low Temperature Fabrication of Lead-Free KNN-BNT Ceramics via the Combustion Technique. *Ferroelectrics* 2014, **458**, 136.
- 50 W. Deng, D. Chen, J. Hu, L. Chen, A general and green approach to synthesize monodisperse ceria hollow spheres with enhanced photocatalytic activity. *RSC Adv.* 2015, **98**, 80158.
- 51 Y. Xu, N. Gao, Y. Gong, S. Huo, M. M. Mohideen, S. Hong, Y. Liu, Controllable preparation of methyltriethoxysilane xerogel nanofibers. *J. Mater. Sci.* 2019, **54**, 10130.
- 52 R. Czochara, J. Kusio, G. Litwinienko, Fullerene C₆₀ conjugated with phenols as new hybrid antioxidants to improve the oxidative stability of polymers at elevated temperatures. *RSC Adv.* 2017, **70**, 44021.
- 53 S. Leach, M. Vervloet, A. Desprès, E. Bréheret, J. P. Hare, T. J. Dennis, H. W. Kroto, R. Taylor, D. R. W. Walton, Electronic spectra and transitions of the fullerene C₆₀. *Chem. Phys.* 1992, **160**, 451.
- 54 R. Signorini, M. Meneghetti, R. Bozio, M. Maggini, G. Scorrano, M. Prato, G. Brusatin, P. Innocenzi, M. Guglielmi, Optical limiting and nonlinear optical properties of fullerene derivatives embedded in hybrid sol-gel glasses. *Carbon* 2000, **38**, 1653.
- 55 K. I. Maslakova, Y. A. Teterin, A. J. Popel, A. Y. Teterin, K. E. Ivanov, S. N. Kalmykov, V. G. Petrov, P. K. Petrov, I. Farnan, XPS study of ion irradiated and unirradiated CeO₂ bulk and thin film samples. *Appl. Surf. Sci.* 2018, **448**, 154.
- 56 T.S. Wu, L.Y. Syu, C.N. Lin, B.H. Lin, Y.H. Liao, S.C. Weng, Y.J. Huang, H.T. Jeng, S.Y. Lu, S.L. Chang, Y.Li. SooWu. Enhancement of catalytic activity by UV-light irradiation in CeO₂ nanocrystals et al. *Scientific Reports*. 2019, **9**, 8018.
- 57 Jee-Hun Maeng and Sung-Churl Choi. The Effect of Cerium Reduction on Light Emission in Cerium-containing 20Y2O3-25Al2O3-55SiO2 Glass. *JOSK*. 2012, **16**, 414.
- 58 A. Bianco, F. Gasparini, M. Maggini, D. Misiti, A. Polese, M.-Prato, G. Scorrano, C. Toniolo, C. Villani, Molecular Recognition by a Silica-Bound Fullerene Derivative. *J. Am. Chem. Soc.* 1997, **119**, 7550.

View Article Online
DOI: 10.1039/D0NA00048E

Open Access Article. Published on 13 April 2020. Downloaded on 4/15/2020 12:56:47 AM.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Nanoscale Advances Accepted Manuscript